




Contents lists available at ScienceDirect

Construction and Building Materials

journal homepage: www.elsevier.com/locate/conbuildmat

Assessing the sustainability potential of alkali-activated concrete from electric arc furnace slag using the ECO₂ framework



Hisham Hafez ^{a,*}, Dany Kassim ^b, Rawaz Kurda ^{c,d}, Rui Vasco Silva ^{b,*}, Jorge de Brito ^{b,*}

^a Department of Mechanical and Construction Engineering, Northumbria University, Newcastle, UK

^b CERIS, Instituto Superior Técnico, Universidade de Lisboa, Portugal

^c Department of Highway and Bridge Engineering, Technical Engineering College, Erbil Polytechnic University, Erbil 44001, Iraq

^d Scientific Research and Development Center, Nawroz University, Duhok 42001, Iraq

HIGHLIGHTS

- Electric arc furnace slag as a novel precursor in alkali-activated concrete.
- Optimization of fresh, mechanical and durability properties.
- Life cycle assessment of concrete mixes based on primary data.
- Sustainability assessment based on economic, ecological, and functional pillars.
- Sustainability index multi-criteria optimization for alkali-activated concrete.

ARTICLE INFO

Article history:

Received 28 September 2020

Received in revised form 5 January 2021

Accepted 30 January 2021

Available online 18 February 2021

Keywords:

Sustainability

Life cycle assessment

Sustainable concrete

Electric arc furnace slag

Alkali-activated concrete

CO₂

ABSTRACT

Alkali-activated materials are regarded as a potential sustainable building material with industrial by-products fully replacing ordinary Portland cement. Five million tonnes of electric arc furnace slag are produced annually mostly to be recycled as low value aggregates in several construction applications. This study examined the possibility of valorising the understudied slag as a precursor in alkali-activated concrete. The material, supplied free and available in abundance as a waste, presents a significant potential to produce sustainable concrete. Hence, the mechanical and durability properties of electric arc furnace slag-based alkali-activated concrete were examined. After that, using a sustainability assessment framework called ECO₂, the combined whole-life cycle assessment of the environmental and economic impact was calculated for several mixes that combined electric arc furnace slag and fly ash as precursors. The increasing amount of slag content led to a decline in mechanical performance, though there was an equivalent durability-related performance; mixes with electric arc furnace slag showed equivalent slump and resistance to carbonation, and enhanced resistance to chloride ion penetration. Furthermore, slag-based concrete exhibited significant improvement in the overall ECO₂ sustainability score due to its minimal environmental and economic impact.

© 2021 Elsevier Ltd. All rights reserved.

1. Introduction

Around 30 billion tonnes of conventional concrete were produced in 2015 [1]. Due to its inherent strength and durability properties, concrete is the second most used substance on Earth after water [2]. The use of concrete is associated with immense negative environmental impacts. The current annual production of >4 billion tonnes of ordinary Portland cement (OPC) is responsible for 7% of

the global CO₂ emissions [3]. Concrete has an environmental impact of 300 kg eq CO₂/m³ on average, of which 90% is attributable to OPC [4]. Although this is less than that of steel and most polymers per unit mass [5], the intensive use of OPC concrete results in alarming environmental hazards. In China, for example, concrete production alone resulted in approximately 1.5 billion tonnes of greenhouse gas (GHG) emissions in 2014 [6], which represents around 20% of the total produced in the same year [7]. Projections indicate that the growing global urbanization could double the demand of concrete by 2050 [8].

Immense efforts are being made to explore the potential of valorising industrial by-products with low recyclability as precursors

* Corresponding authors.

E-mail addresses: hisham.hafez@northumbria.ac.uk (H. Hafez), rawaz.kurda@tecnico.ulisboa.pt (R. Kurda), rui.v.silva@tecnico.ulisboa.pt (R.V. Silva), jb@civil.ist.utl.pt (J. de Brito).

of OPC-free binders in alkali-activated concrete (AAC). While an OPC paste is a mixture of Portland cement and water, an AAC mix consists of a precursor and an alkali activator solution. The most well-known activators are sodium hydroxide (SH) and sodium silicate (SS), while fly ash (FA), ground granulated blast furnace slag (GGBS) and calcined clay are recognized precursor types. The strength and durability of an AAC are highly dependent on the quality of the binder, which is determined by three main aspects: 1) the curing method - in Puertas et al. [9] it is argued that dry-sealed curing optimizes the properties of AAC, while in Nasir et al. [10] the significance of heat curing for AAC with several pozzolanic material is emphasized, especially that with FA as a precursor for the first 24 h; 2) the reactivity of the precursor - the smaller the particle size and the more amorphous the precursor is, the more reactive it is expected to be [11]; 3) the chemical compatibility of the reactants - a precursor is a material with an abundance of either calcium, aluminium or silicon oxide, as shown in Fig. 1. It was found that the following four ratios are critical to the functional properties of the AAC mix [12]:

- The mass ratio of solution to the precursor;
- The Si/Al ratio of the chemical composition of the precursor;
- The concentration of the alkali activating solution (Na₂O %);
- The ratio between SiO₂/Na₂O in the alkali activator (MS).

Most AAC mixes have higher workability than OPC concrete [14], but it is more susceptible to loss after short periods if it presents a high SiO₂/Na₂O ratio. However, AAC is not compatible with most of the commercially available water-reducing agents, which are fundamental to increase the workability beyond a given threshold of the solution to precursor ratio [15]. The compressive strength of an AAC mix can be higher than that of OPC concrete, but the higher the solution concentration (Na₂O %) in a NaOH activator, the higher the strength of the FA-based AAC [16]. Regarding

GGBS-based AAC mixes, it was confirmed that the silica modulus is an essential parameter for optimizing the mechanical properties of the resulting AAC [17]. Concerning the resistance to chloride ion penetration, AAC is typically more durable than OPC concrete, but is also highly dependent on the SiO₂/Na₂O ratio in the activator, as well as the ratio of activator/precursor [18]. Finally, it has been established that most AAC mixes are generally less resistant to carbonation than OPC concrete, but are still highly dependent on the optimization of the chemical ratios, as discussed before [19]. Nasir et al. [20–22] observed that admixing 30% slag with the main precursor material, with a 10 M solution of NaOH and Na₂SiO₃/NaOH ratio of 2.5, and lower temperature curing favour the densification of the microstructure leading to a reduction in carbonation.

According to Jiang et al. [23], the embodied carbon of an AAC mix is around 50% less than that of an OPC mix. Moreover, industrial by-products are usually cheaper than OPC, which further enhances the sustainability potential of AAC [24]. However, this trend may not be generalized in terms of the environmental and economic impact of all AAC alternatives. The reason is that SS and SH, the main components of the alkaline activator solutions in AAC, are expensive and energy-intensive in production [25]. Another reason is that, in several cases, some energy is required to either prepare the industrial by-product by crushing and milling or when heat curing the AAC [26]. The use of SS and SH also causes a 10-fold increase in human toxicity, ecotoxicity of freshwater bodies and ozone layer depletion potential (ODP) in comparison to conventional OPC-based concrete mixes [4]. However, the ODP impact of 1 kg of cement is insignificant when contextualized to the greater environmental ecosystem since it equals the impact of a household light bulb in a month [27].

Most of the steel production worldwide is shifting towards electric arc furnaces (EAF) because it requires less energy and cost [28]. EAF production technique took over 55% of the market in the US in

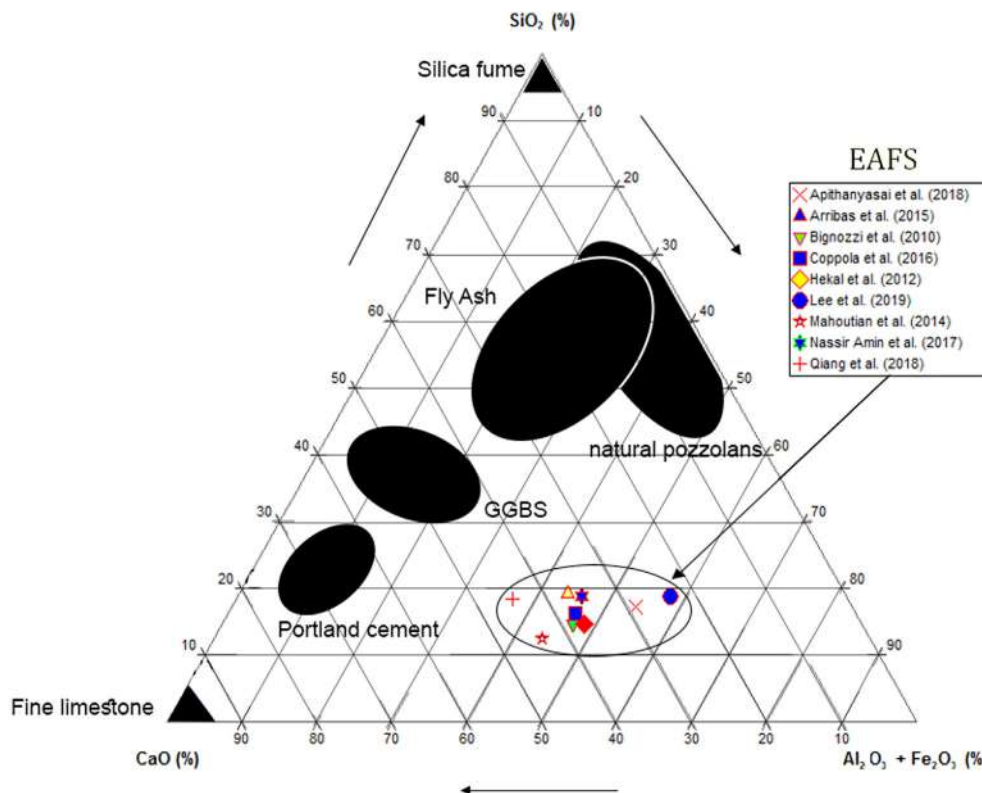


Fig. 1. Ternary diagram with the chemical composition of possible precursors for AAC (adapted from Lothenbach et al. [13]).

2006 [28]. Considering that 50 million tonnes of EAF steel are produced worldwide, around 5 million tonnes of EAFS (~10% of the total amount of EAF steel) are generated in the process [29]. Contrary to GGBS, EAFS are mostly recycled as low-value road embankments [30]. Hence, there is a significant potential for recycling EAFS as a precursor in AAC. In order to assess the suitability of recycling EAFS in binders, the following facts were found in the literature:

- The chemical composition: EAFS mainly consists of 25–40% of iron oxides, 25–40% of calcium oxides, 10–30% of silicon oxides and 5–15% of aluminium oxides (Fig. 1). This means that there is abundance in aluminosilicate and EAFS could qualify as a precursor. However, the presence of free CaO provides a threat to its integration in concrete due to risk of volumetric instability [31];
- The physical characterization of EAFS without treatment shows an almost crystalline microstructure, which indicates low reactivity [32]. The reason is that the molten slag is dumped upon formation and is allowed to air cool over a long time.

As received, EAFS is dark in colour, with angular shaped fractions of a hard and rough surface, which makes it adequate for use as an aggregate in concrete [28]. The density of EAFS varies between 3000 and 3500 kg/m³, which is 20–30% higher than that of natural aggregates due to the presence of iron and iron oxides [33]. Concrete mixes, in which EAFS was incorporated as coarse aggregates, were found to exhibit lower strength [31]. The higher replacement level of coarse natural aggregates with EAFS, the lower the workability and the higher the shrinkage of concrete [34]. This is because EAFS absorbs 20–30% more water than that of the natural aggregates [35]. Studies showed that integrating EAFS as a partial replacement of OPC up to 20% in blended cement concrete would yield the same compressive strength [36]. For higher replacement ratios, the strength and durability of concrete decreases due to the established low pozzolanic activity [37]. However, further mechanical activation of EAFS; which can be achieved through grinding it to $d_{90} = 11 \mu\text{m}$, can increase the replacement ratio up to 30% [38]. The energy required to grind EAFS to the required particle sizes was reported to be 68 kWh/tonne [39]. In addition, re-melting and then quenching of the EAFS could result in a more amorphous microstructure, which would enhance the pozzolanic properties of the slag [40]. However, the initial idea behind recycling EAFS in concrete was to decrease the environmental impact, so special attention is needed when energy-intensive processes are required. When it comes to alkali-activated binders, only a few studies were carried out on the use of EAFS as a precursor in alkali activation [41,42]. In Apithanyasai et al. [41] an alkaline solution was prepared using 10 M concentration and a silica modulus of 2.5 and the solution/precursor ratio was of 0.9. The compressive strength of the EAFS-based alkali-activated paste was 30% less than that of the control OPC paste but the water absorption and shrinkage were compatible. In addition, Ozturk et al. [42] ran an optimization scheme on several mortar mixes and concluded that the optimum mixes for compressive strengths were obtained when the Na₂O concentration, SiO₂/Na₂O ratio and early age curing temperature were set at 6%, 2 and 80 °C, respectively.

There is a clear need for researching the properties of concrete with sustainability potential such as the proposed EAFS-based AAC. As for environmental impacts, although EAFS is a waste and carries minimal impact aside from transportation, processing the slag to increase its reactivity through mechanical activation is an energy intensive process. The same applies to increasing the sodium concentration in the alkali activator to enhance the functional properties of EAFS-based AAC. In terms of economics, EAFS can be

supplied for free [41]. This shows sustainability potential in terms of economic and environmental impact when recycled as a precursor for AAC. However, the functional parameters are still uncertain given the variability in the chemical composition of EAFS and the scarce publications in this regard. FA-based AAC could show satisfactory performance in terms of functional impact depending on the optimized mix design parameters. Therefore, it was decided to use a combination of FA and EAFS as a precursor to produce an optimized mix. Table 1 summarizes the outlines for the optimum mix design from the literature.

In a publication of the authors [43], a concrete sustainability assessment framework - ECO₂ - was developed. ECO₂ is primarily a performance-based multi-criteria decision analysis framework that defines sustainability as the user-weighted average of the economic and ecological impact of concrete based on specific functional requirements. The framework as seen in Fig. 2, builds on user-defined performance criteria such as minimum slump, strength and a target service life. Based on primary data, the framework performs a life cycle assessment to calculate the environmental and economic impact using parameters such as: global warming potential, ozone layer depletion and net present value of money. The framework, which will be used to assess the sustainability of the studied AAC mixes in this paper, then calculates the sustainability index, the ECO₂ score, as a weighted average between the aggregated impacts of both pillars.

2. Materials and methods

2.1. Materials

- Electric arc furnace slag:

The slag (Fig. 3a) was acquired from the Siderurgia Nacional company, Portugal, with an extensive particle size distribution. A three-step mechanical activation process was followed. In the first step, the slag was crushed using a Los Angeles abrasion testing machine, then using a jaw crusher and finally a ball mill. The resulting material (Fig. 3b) showed an average particle size of ~25 μm. The chemical characterization of the slag, obtained using X-ray fluorescence (XRF), is presented in Table 2.

- Fly ash:

FA was acquired from a coal power plant in Sines, Portugal. The as-received FA had an average particle size of ~15 μm. The chemical composition of the FA is shown in Table 2.

- Alkaline solution:

To prepare the alkaline solution, pure NaOH pellets (99% purity) were acquired from a local supplier in Lisbon. A commercial superplasticizer (SP) that consists of a β-naphthalene sulfonic acid formaldehyde condensate was added to the alkaline solution before mixing. Tap water was used as solvent.

- Aggregates:

Five grades of natural aggregates were procured from different local sources. Two sizes of natural silica sand were used as fine aggregates and three sizes of crushed limestone were used as coarse aggregates. The particle size ranges, proportions and the water absorption of are summarized in Table 3. The particle size distribution of the aggregates comply with the requirements of ASTM C33 [44].

Table 1
A summary of the effect of critical parameters of the mix design of AAC on sustainability indicators.

Parameter	Interpretation	Action	Predicted effect on the AAC sustainability parameters				
			Functional Workability	Strength	Durability	Environmental	Economic
Particle size of the precursor	Lower sizes increase reactivity	Mechanical activation	NA	↑	↑	↑	↑
Mineral characteristics of precursor	More amorphous phases increase reactivity	Re-melting and quenching	NA	↑	↑	↑	↑
Alkalinity of precursor (Kb)	If > 1, a base optimum Ms = 1.00–1.5 If < 1, an acid optimum Ms = 0.75–1.25	The more SS used, the higher the Ms	↓	↑	↑	↑	↑
Silica modulus (Ms) = SiO ₂ /Na ₂ O	-	-	-	-	-	-	-
Alkaline concentration (%) = Na ₂ O	-	The more SH used, he higher the % of sodium oxide in the solution	NA	↑	↑	↑	↑
Solution: Precursor ratio	Optimum ratio around 0.4	Decrease the ratio	↓	↑	↑	↓	↓
EAFS / FA ratio	Replacement (%) of FA by EAFS as a precursor	Increase the ratio	↑	↑	↑	↑	↑

Notes: Improvement - ↑↓; Deterioration - ↓↑; Not applicable - NA

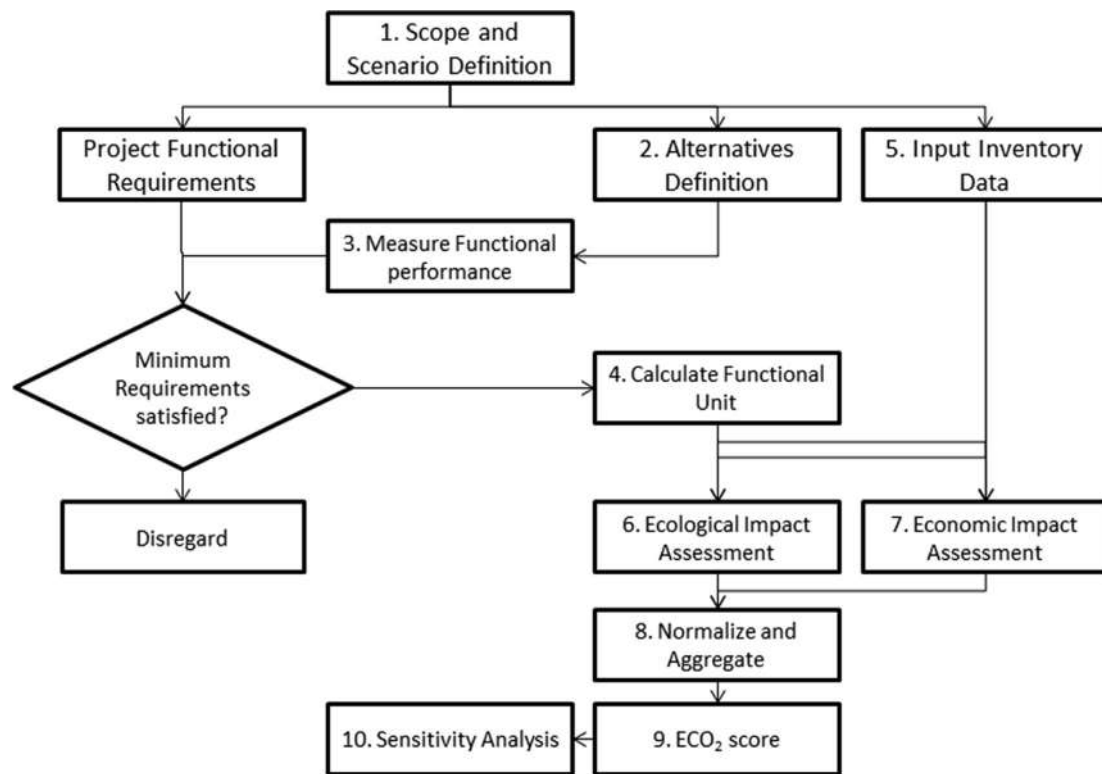


Fig. 2. A basic flowchart for the ECO₂ algorithm.

2.2. Concrete mix design

An experimental program was developed for the mixes shown in Table 4. Mixes 1–3 consist of precursors of 100% FA as a reference AAC because they are established in the literature, while mixes 7–9 are based on 100% EAFS precursors. To gain the co-benefits, mixes 4–6 were produced with proportions of 50% FA and 50% EAFS as precursors. Based on data from the literature, it was decided that synthesizing alkaline solution with a concentration of 10% Na₂O to binder would yield the optimum concrete performance. The literature also suggests that the optimum activator

for slag would be a SiO₂/Na₂O ratio close to 2. However, it was decided not to include SS in the mix to maintain a low level of economic and environmental impacts. The water to precursor ratio varies between 0.30, 0.40 and 0.50 and the content of SP varied according to the results of trial mixes to target a S3/S4 slump class.

2.3. Concrete mixing, casting and curing procedures

The alkaline solution was prepared by dissolving the SH pellets in water gradually and then left to cool down for 24 h. On the mixing day, the solution was added first in the mixer along with the SP



Fig. 3. EAFS as-received (left) and after milling to the required size for use as a precursor in concrete (right).

Table 2

X-ray fluorescence results of EAFS and FA.

Material	CaO (%)	SiO ₂ (%)	Al ₂ O ₃ (%)	Fe ₂ O ₃ (%)	MgO (%)	SO ₃ (%)	Na ₂ O (%)	K ₂ O (%)	LOI (%)
EAFS	25.5	16.0	9.16	25.7	5.12	0.3	0.17	0.03	9.63
FA	3.6	57.8	20.9	7.4	1.0	0.6	1.0	1.7	3.8

Table 3

Characterization of the aggregates used in the concrete mixes.

Aggregates	Nominal size mm	Oven-dried density (kg/m ³)	Water absorption %	Mass ratio of total fine/coarse aggregate content %
Fine sand	0/1	2637	0.4	30
Coarse sand	0/4	2617	0.5	70
Rice grain gravel	2/5.6	2600	1	15
Fine gravel	5.6/11.2	2600	1.2	25
Coarse gravel	10/20	2600	1.4	60

Table 4

Mix design of mixes 1–9.

Components	Mass of each component per AAC mix (kg/m ³)								
	M1	M2	M3	M4	M5	M6	M7	M8	M9
FA	299	292	284	150	146	142	0	0	0
EAFS	0	0	0	167	163	158	334	325	316
SP	4	1	0	5	1	0	5	3	2
Water	104	131	155	104	131	155	104	130	155
NaOH	39	38	37	41	40	39	43	42	41
Fine sand _{0/1}	265	258	251	265	258	251	264	257	250
Coarse sand _{0/4}	613	597	581	613	597	581	612	595	579
Sand-Gravel _{2/5.6}	174	169	165	174	169	165	174	169	164
Fine gravel _{5.6/11.2}	290	282	275	290	282	275	290	282	274
Coarse gravel _{10/20}	696	678	660	696	678	659	695	676	658
Mix design ratios									
Effective water/ precursor	0.3	0.4	0.5	0.3	0.4	0.5	0.3	0.4	0.5
SP/ precursor (%)	1.5	0.5	0	1.5	0.5	0	1.5	1	0.5
FA/ precursor (%)	100			50			0		
EAFS/ precursor (%)	0			50			100		
Na ₂ O/ precursor (%)	10								

and the precursor and then mixed for 5 min. After that, the mixer was stopped until the aggregates were added and then all the components were mixed together for another 5 min. After the slump test was carried out, the moulds were sprayed with paraffin and concrete was cast inside and vibrated according to EN 12390-2 [45]. After casting, the specimens were wrapped with thin plastic film for sealing, and then placed in a thermal curing chamber. Specimens were cured for the first 24 h in an oven at 70 °C. Afterwards, the specimens were demoulded and left to cure in a cham-

ber with a temperature of 23 ± 2 °C and a relative humidity of 100% until testing day.

2.4. Hardened concrete test methods

- Slump:

The slump test was performed on each fresh mix according to the EN 12350-2 standard [50]. Mixes with a slump < 100 mm were rejected and the SP was adjusted accordingly.

- Compressive strength:

After 28 days of curing, 150 mm cubic samples were tested for compressive strength according to the EN 12390-3 standard [50] using a TONI PACT 3000 universal testing machine with a 12 kN/s loading rate.

- Chloride ion penetration:

After 28 days of curing, three cylindrical specimens of 100 mm in diameter and 50 mm in thickness per concrete mix were cut from the cast cylinders. As per the BUILD NT 492 standard [47], the specimens were placed in a clean and dry desiccator and air vacuumed for 3 h. After that, the samples were vacuumed in a lime solution for 1 h then left for 20 more hours to saturate in the lime solution. On testing day, the specimens were placed in sealed rubber forms and then in the rapid chloride ion penetration testing (RCPT) apparatus. The chloride diffusion coefficient of each specimen D_{nssm} was then calculated using the equation from the standard.

- Carbonation:

After 21 days of curing, six cylindrical specimens of 100 mm diameter and 30 mm thickness were cut from the originally cast samples of each mix following the LNEC E391 standard [48]. At 28 days, two specimens of each mix were placed in a carbonation chamber with a CO₂ concentration of 5 ± 0.1%, temperature of 23 ± 3 °C and relative humidity of 60 ± 5% for 14 days. After the exposure period ended, the samples were broken into four pieces and sprayed with phenolphthalein. The depth of carbonation was then measured using a Vernier calliper across each face of the broken fraction of each sample and averages were recorded for every mix.

2.5. Applying the ECO₂ framework

2.5.1. Scope and scenarios

ECO₂ framework is applied in 10 steps as in Fig. 4, are divided between two stages.

The first stage includes: defining the scope and the scenarios; defining the alternative, and collecting the necessary inventory data. After that, the second stage includes calculating the functional unit for each alternative, assessing the environmental and economic impact and finally the ECO₂ index is evaluated in an attempt to optimize the alternatives. In a typical LCA study, the scope for a concrete product life cycle could be Cradle-to-Gate, which means including all processes and emissions until the production of its different constituents or Cradle-to-Grave, which includes the “Use” and “End-of-Life” phases. In this study, as in Fig. 4, it was decided to have a Cradle-to-Gate scope, due to the similarity in the remaining processes across all alternatives.

To account for uncertainty as per the LCA recommendations, two scenarios were defined: a reinforced concrete scenario (S1) and a plain/mass concrete scenario (S2). The former would account for the durability of concrete alternatives under study, while the latter would assume the AAC fulfils the service life requirements. Since Eurocode 2 specifies a minimum of 10 MPa for the characteristic compressive strength of cubic specimens, this value was set as the required compressive strength (threshold value) of both concrete scenarios. Preliminary testing showed very low strength values obtained from testing mixes 7, 8 and 9, they would not fulfil the basic project requirements and, hence, are excluded from the comparison. The comparison between the remaining six alternatives (M1-M6) was based on a unit

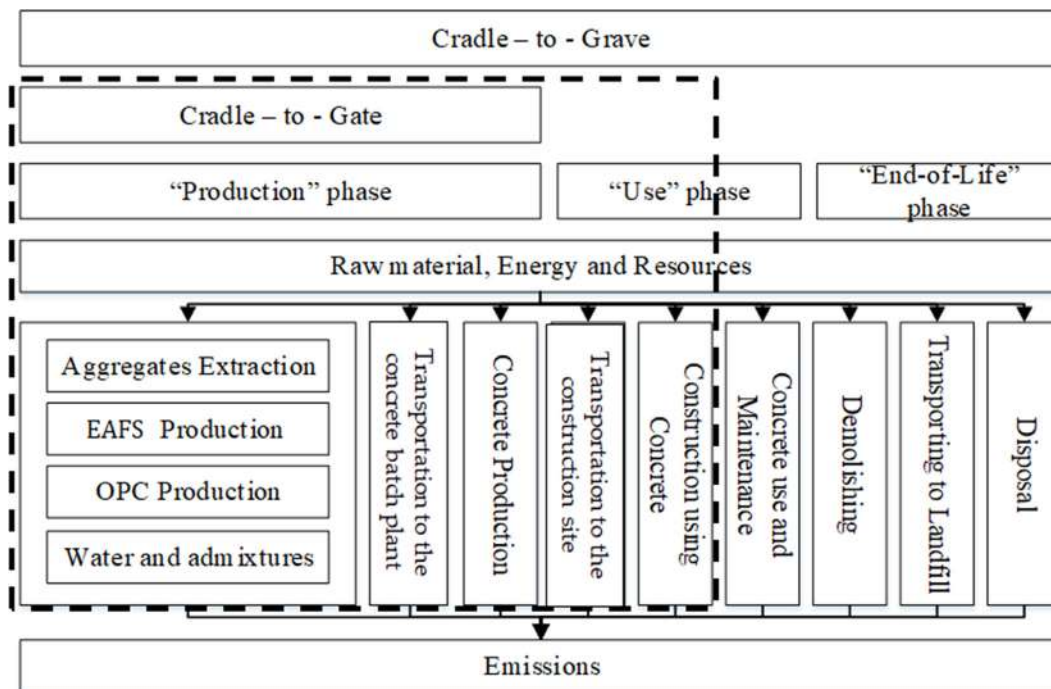


Fig. 4. Typical LCA boundary and the scope selected for this study.

Table 5
Summary of the environmental and economic inventory data for the LCA study.

	Market price per unit	Distance	GWP	ODP	AP	EP	ADPE	POCP	CED	FW
	€ per unit	km	kg·co ²	kg·cf ^c ·t ⁻¹	kg·so ²	kg·po ⁴	kg·sb _{eq}	kg·c2H _{4eq}	MJ	m ³
Electricity from coal (/kWh)	-	-	3.19E-01	7.70E-10	1.83E-03	2.96E-04	2.60E-03	7.09E-05	9.10E-04	3.75E + 00
Portuguese unit energy impact (/kWh)	0.11	-	3.75E-02	1.59E-09	0.00E + 00	1.08E-04	2.79E-04	6.65E-06	8.30E-01	2.93E-01
Impact per distance (/km)Small truck (<25 tonnes)	0.05	-	2.90E-01	1.90E-07	7.60E-05	1.67E-04	8.14E-04	6.11E-05	3.15E + 00	3.62E-01
Binder (/kg)	0	30	3.11E-03	1.32E-10	0.00E + 00	9.00E-06	2.31E-05	5.52E-07	6.89E-02	2.43E-02
Fly ash (0.3% allocation)	0.036	15	9.56E-03	2.31E-11	5.48E-05	8.88E-06	7.79E-05	2.13E-06	2.73E-05	1.13E-01
Aggregates (/kg)	0.01	15	1.03E-02	1.05E-09	1.53E-05	5.39E-06	1.49E-05	4.53E-06	7.19E-02	2.90E-02
Natural coarse	0.01	20	6.72E-03	4.75E-08	8.10E-06	2.82E-06	5.07E-05	9.83E-07	5.78E-02	2.11E-02
Natural fine	1.4	100	9.08E-01	1.09E-07	5.44E-02	9.24E-04	4.94E-03	1.88E-04	1.98E + 01	6.98E-01
Chemical admixtures - Superplasticizer (/kg)	0.51	0	1.27E + 00	1.14E-07	2.93E-03	6.63E-04	9.30E-03	2.61E-04	6.35E + 00	2.24E + 00
Activator (/kg)	0.277	0	2.50E-04	5.57E-12	0.00E + 00	1.26E-07	6.83E-07	6.32E-08	2.95E-04	1.06E-03
Water										

ADP - Abiotic depletion potential; AP - Acidification potential; EP - Eutrophication potential; GWP - Global warming potential; POCP - Photochemical ozone creation potential; CD - Cumulative energy demand; FW - Fresh water use

volume of concrete that has a minimum slump of 100 mm and a targeted service life of 50 years.

2.5.2. Definition of alternatives

The next step would be to enter the mixing proportions of each mix (conventional and non-conventional/alternative mixes) per cubic meter as per the mix design in Table 4. This would then serve as the basis for quantifying the environmental and economic impact of each alternative as per the ECO₂ logic.

2.5.3. Environmental inventory data

- Raw materials production

The only primary production data collected for this study is the energy required for EAFS processing. For every 20 kg, the LA abrasion testing machine was used for 2 h, then the jaw-crushing machine was used for 1 h and finally the ball-milling machine was used for 2 h. The power input for each of these machines is 800 W, 500 W and 1200 W, respectively. Hence, the energy demand allocated for the production of each kg of EAFS is calculated as follows. Slag processing energy = (2 h × 0.8 kW + 1 h × 0.5 kW + 2 h × 1.2 kW) / 20 kg = 83 kWh/tonne. This is translated to the environmental indicators by multiplying it by the average impact per unit energy of the Portuguese energy grid. The inventory data concerning the unit energy and the data concerning the production of the remaining concrete constituents are averages from a secondary database that was published in a systematic literature review [49], as seen in Table 5.

- Raw materials transportation

All materials were produced in Portugal and transported locally, using a small truck. An extra 70% of the impact is added to account for the return ride. The transportation distances are summarized in Table 5.

- Concrete construction

The energy and emissions involved in the concrete construction phase are the combination of that resulting from mixing, transporting to site, casting and curing. The curing method followed for all AAC mixes within the scope of this experimental campaign included 24 h in the thermal curing chamber. The chamber, operating at 70 °C, used a heating unit with an input power equal to 2000 W. The oven has a capacity of approximately 25 cubes (150 mm), which means that the energy required for curing could be calculated as: concrete curing energy = 2 kW × 24 h / (25 cubes × 0.15 m × 0.15 m × 0.15 m) = 20 kWh/m³. The energy required for the mixing and placing concrete was assumed as 20 kWh/m³ and the distance from the batch plant to the site as 80 km. The aforementioned data was estimated based on the secondary database in [49].

2.5.4. Economic inventory data

The economic impact of the production of a concrete mix is basically the sum of the costs of the production and transportation of all its constituents. However, similarly to the ecological impact calculations, in order to account for the whole life cycle of concrete, the economic impact for every concrete mix needs to also include that of the transportation of concrete to the construction site as well as the processes of construction and demolition.

The primary data provided by the suppliers for the purchasing prices of all constituents of the AAC studied was added to the ECO₂. The cost of transporting the raw materials to the concrete batch plant was calculated based on an average unit price for

transportation from the database in [45]. It is important to note that, unlike the environmental impact calculations, the return distance was not accounted for because it is assumed as included in the price. The summary of the data is found in Table 5.

2.5.5. Functional unit calculations

The functional unit (FU) is a key element in a LCA and is responsible for the quantification of the environmental and economic impact indicators [49]. In most sustainability frameworks, the functional unit is assumed as simply a unit volume of concrete (1 m³). However, calculating the FU according to the ECO₂ framework is done in two stages. The first is checking whether the minimum requirements of the project, which are workability and strength, are met. For every alternative (i), the user inputs the values for slump (Yslump) and strength (Ystrength) and if Yslump (i) < Yslump (required) or Ystrength (i) < Y strength (required), the alternative is rejected. Note that, as explained in the scenario definition, the required slump and strength for this case study are 100 mm and 10 MPa respectively. If an alternative achieves the minimum requirement, the functional unit is defined as per the following equation (1), where N is the replacement ratio of the concrete alternative, reflecting the number of times it would need to be replaced to fulfil the required service life. If the concrete alternative is plain concrete, which is the case in scenario 1, it is assumed as durable enough to sustain itself throughout the required service life without need for maintenance or replacement. Hence, in scenario 1, for all 6 alternatives, N is equals to 1 and FU is equals to 1 m³ of concrete.

$$FU_i = N_i * 1m^3 \quad (1)$$

For each reinforced concrete alternative in scenario 2, N is calculated as per equation (2) where SL_R is the required service life, which is 50 years in this case. SL_{p-cl} and SL_{p-cr} are the predicted service life for this alternative against chloride-induced corrosion and carbonation-induced corrosion respectively.

$$N = \frac{SL_R}{\min(SL_{p-cl}, SL_{p-cr})} \quad (2)$$

The main durability parameters of concrete are the resistance to chloride penetration and carbonation [49]. Hence, these are the ones considered within the ECO₂ framework to predict the service life of concrete. Service life predictions against chloride-induced corrosion are defined in standards as the duration that the chloride content at the surface of the steel reinforcement takes to reach the chloride threshold [46]. The model, developed based on Fick's 2nd law of diffusion, predicts the service life SL_{p-cl} as per equations (3) and (4) at the time when C(x, t) is equal to C_{cr}:

$$C(x, t) = C_o * \operatorname{erfc}\left(\frac{x}{2 * \sqrt{D_t * t}}\right) \quad (3)$$

$$D_t = D\left(\frac{t_o}{t}\right)^\alpha \quad (4)$$

Where, D is the chloride diffusion coefficient (m²/s), C_{cr} the chloride threshold level (%), C_o the chloride concentration on the concrete surface estimated at 1%, X the concrete cover assumed as 70 mm in this case study, α an aging factor, and t the service life expected for the durability against chloride penetration SL_{R-cl}, in years.

$$SL_{p-cr} = \left(\frac{X}{K_n}\right)^2 \quad (5)$$

$$K_n = K_a \sqrt{\frac{CC_n}{CC_a}} \quad (6)$$

The durability of a concrete alternative against carbonation is a measure of the time at which the depth of carbonated concrete (X_c) is equal to the concrete cover (X). Hence, the model used to predict the service life of concrete alternatives depends on K_n, which is the natural carbonation rate of concrete, to calculate SL_{p-cr} as seen in equation (5). In cases such as this study where an accelerated carbonation test is performed, K_n is correlated to the accelerated carbonation rate K_a using equation (6). The values for CC_n, which is the CO₂ % concentration in the environment and CC_a, which is that in the carbonation chamber in which the test was done are 0.05% and 5% respectively.

2.5.6. Ecological impact calculations

The first step is to calculate the impact of producing concrete per unit volume is by multiplying the impact of producing and transporting every constituent by its mixing proportion for every alternative. The second step is to add the impact from concrete construction as per equation (7). The environmental impact is demonstrated through eight mid-point indicators: Global Warming Potential (GWP), Ozone Depletion Potential (ODP), Acidification Potential (AP), Eutrophication Potential (EP), Abiotic Depletion Potential (ADPE), photochemical ozone creation potential (POCP), Cumulative Energy Demand (CED) and Fresh Water (FW).

$$\frac{GWP_i}{m^3} = \sum_{j=1}^n \left(\frac{GWP_{jupstream} * kg_j}{kg} * \frac{kg_j}{m^3} \right) + \frac{GWP_i construction}{m^3} \quad (7)$$

The total impact per unit volume is then multiplied by the functional unit of each alternative. Once the total impact per functional unit is calculated for each alternative, it is then normalized, according to equation (8), with the alternative with the lowest impact in each indicator getting a value of 1 and the one with the highest impact a value of 0. Finally, the single environmental indicator, which is called the ecological indicator within to the ECO₂ algorithm, is calculated based on the weighted average of all eight indicators.

$$V'_i = \frac{\max(V_i) - V_i}{\max(V_i) - \min(V_i)} \quad (8)$$

2.5.7. ECO₂ index calculations

After calculating the single ecological indicator for each alternative, the single economic indicator is calculated as such. Using the economic inventory data, the per unit volume total cost of each alternative is calculated by summing up the cost of production and construction. After that, the single economic indicator Z is calculated as the FU of each alternative multiplied by the total cost per unit volume.

The single economic indicator Z is then normalized using the same equation (8) with the cheapest alternative getting a score of 1 and the most expensive as 0. The ECO₂ index is then calculated for each alternative as an average of the scores of its normalized single ecological index V and the economic one Z as per equation (9).

$$ECO_{2i} = V_i * 0.5 + Z_i * 0.5 \quad (9)$$

3. Results and discussion

3.1. Functional unit results

For the 6 mixes that were fulfilling of the minimum requirements (slump > 100 mm and strength > 10 MPa), the results of the experimental work show the following. First, as expected, the higher the water to precursor ratio, the higher the workability of

the mix. However, the slump results show no clear correlation between the changes of the precursor from FA to EAFS. The 28-day compressive strength results show that replacing FA with EAFS as a precursor in the AAC resulted in a decrease in strength, mostly due to the lower amount of amorphous silica phases in the latter. In addition, in the 100% FA mixes (M1-3), the higher the water/precursor ratio, the lower the strength.

As seen in Fig. 5, mixes with 50% EAFS as a precursor (mixes 4–6) have around 50% lower chloride diffusion coefficient. The enhanced resistance to chloride penetration could be attributed to the denser microstructure of the EAFS based binder from the literature [36]. This resulted in longer expected service life for these mixes (180 years) compared to that of the 100% FA mixes (100 years).

As seen in Fig. 6, the results of this experiment show that the higher the water/precursor ratio, the higher the carbonation rate. The same applies for replacing FA with EAFS as a precursor, i.e. the higher the replacement ratio, the lower the resistance to carbonation of the AAC mix is. Hence, the expected service life against carbonation for the 50% EAFS mixes (4–6) was around 50% lower than that of mixes 1–3 as seen in Table 6. As a result, the functional unit for mixes 1–3 was 1.3, 1.4 and 1.5 respectively, while that of mixes 4–6 was 1.8, 1.9 and 2 respectively, which affects the impact assessment linearly.

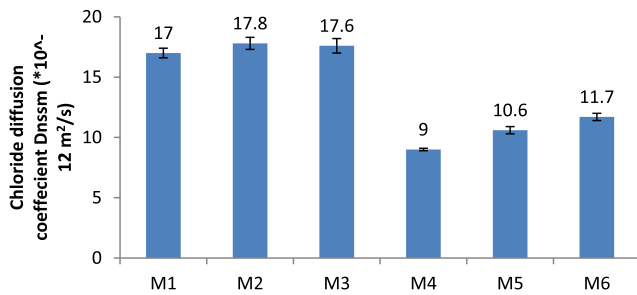


Fig. 5. Chloride diffusion rates of the AAC mixes tested.

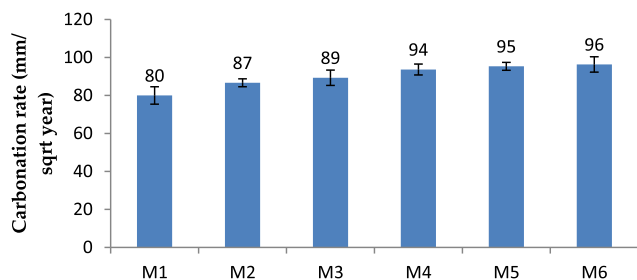


Fig. 6. Accelerated carbonation rate of the AAC mixes tested.

Table 6

A summary of the experimental results and functional unit calculations of mixes 1–6.

Alternative number		1	2	3	4	5	6
1. Slump	mm	105	200	180	110	190	170
2. 28-day compressive strength	MPa	24	19	14	12	11	10
3. 28-day diffusion coefficient (D_{nssm})	$\times 10^{-12} \text{ m}^2/\text{s}$	17	17.8	17.6	9	10.6	11.7
4. Accelerated carbonation rate	mm/ $\sqrt{\text{year}}$	82	85	88	94	97	100
5. Natural carbonation rate	mm/ $\sqrt{\text{year}}$	8.2	8.5	8.8	9.4	9.7	10
Predicted service life as per chloride penetration	Years	100	100	100	180	170	160
Predicted service life as per carbonation	Years	37	35	32	28	27	25
Replacement ratio (N)	-	1.3	1.4	1.5	1.8	1.9	2.0
Functional unit	m^3	1.3	1.4	1.5	1.8	1.9	2.0

3.2. Impact assessment

3.2.1. Ecological impact assessment

- Scenario 1 (plain concrete):

All mixes are assumed to fulfil the service life requirements and hence have an equal FU of 1. As seen in Fig. 7, the contribution of the transportation impact to the total impact of each constituent of the AAC mixes was minimal. Therefore, the comparison between alternatives is purely dependant on the environmental impact of the concrete constituent's production impact.

Due to the higher impact of SP, SH and FA compared to water and EAFS, increasing the W/P ratio and replacing FA with EAFS as precursors yields a binder with a better (lower) environmental impact. As seen in Fig. 8, mixes 4–6 with 20% EAFS showed 60–70% better (lower) environmental impact scores on average compared to mixes 1–3 with 100% FA. The same is observed for mixes 3 and 6 with a W/P of 0.5 compared to mixes 1 and 4, respectively.

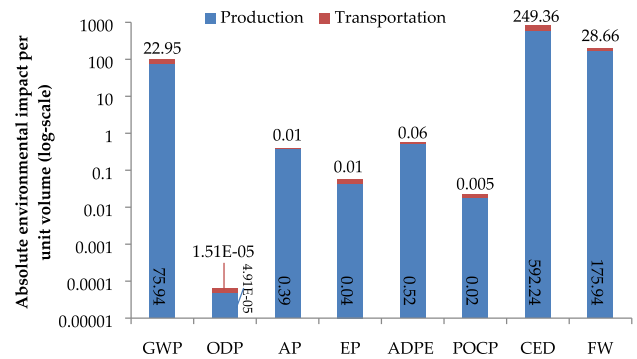


Fig. 7. Contribution of transportation processes to the total environmental impact of alternative 1.

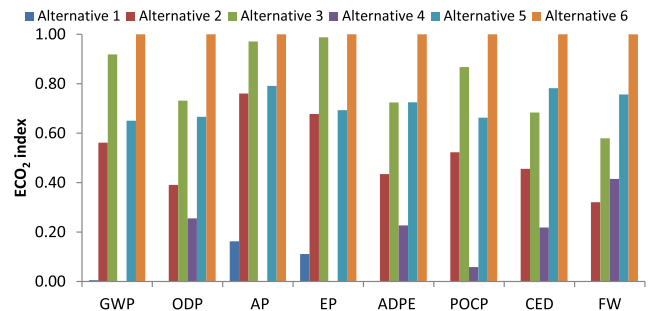


Fig. 8. Normalized environmental impact indicators for plain concrete scenario.

- **Scenario 2 (reinforced concrete):**

Due to the lower carbonation resistance of the mixes with EAFS, mixes 4–6 were calculated to have a functional unit of 1.8, 1.9 and 2 respectively in the 50 years reinforced concrete scenario as opposed to 1.3, 1.4 and 1.5 for mixes 1–3. Hence, the environmental impact of the EAFS was almost doubled which overcame the advantage observed in the plain concrete scenario as seen in the normalized environmental impact scores in Fig. 9.

3.2.2. Calculation of the ECO₂ index

- **Scenario 1 (plain concrete):**

As seen in Table 5, the constituents with the highest environmental impact, FA, NaOH and the superplasticizers, also happen to have the highest cost. Hence, as seen in Fig. 10, mixes with higher W/P ratios (mix 3 compared to 1 and mix 6 compared to 4) and 50% replacement of FA with EAFS (mixes 4–6 compared with mixes 1–3) scored a higher (cheaper) single economic impact indicator. Since this is aligned with the single ecological score comparison, the ECO₂ score followed the same trend.

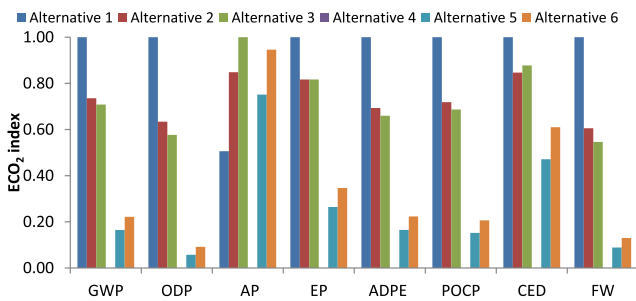


Fig. 9. Normalized environmental impact indicators for plain concrete scenario.

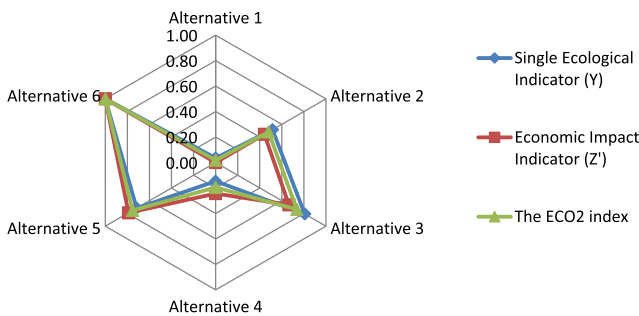


Fig. 10. Single Ecological, Economic and ECO₂ score comparison in scenario 1.

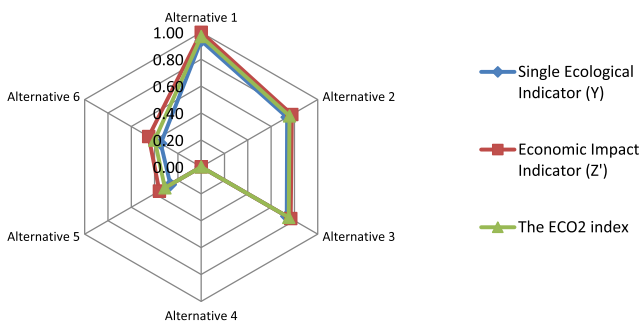


Fig. 11. Single Ecological, Economic and ECO₂ score comparison in scenario 2.

Table 7

Comparison between the GWP, CED and cost of the studied alternatives against global thresholds.

Scenario	Global warming potential kg CO ₂ /m ³	Energy consumption MJ/m ³	Total cost €/m ³
Alternative 1	87.71	841.61	73.4
Alternative 2	81.11	761.47	67.7
Alternative 3	76.80	721.49	64.9
Alternative 4	85.29	803.23	70.3
Alternative 5	77.59	704.13	63.3
Alternative 6	73.23	665.84	60.6
Very High	> 522	> 3388	> 82
High	392–522	2541–3388	75–82
Normal	354–392	2299–2541	69–75
Low	224–354	1452–2541	62–69
Very Low	< 224	< 1452	< 62

- **Scenario 2 (reinforced concrete):**

In the reinforced concrete scenario, mixes 1, 2 and 3 with 100% FA appear to have a far superior sustainability score as seen in Fig. 11 because the advantage in the economic and environmental impact for mixes 4–6 was offset by the major disadvantage in terms of the functional unit. The reason is that, following the literature recommendations, the optimum activators for slag-based precursors require a SiO₂/Na₂O ratio between 1 and 2. However, this would have meant adding SS and increasing the environmental and economic impact. Both of these observations are consistent with the hypothesis provided in Table 1.

3.3. Discussion of the results

3.3.1. Contextualizing absolute impact

Besides the local comparison between the alternatives, a comparison was made in Table 7 against values of global thresholds from Kurda et al. [51] for selected indicators: GWP, CED and basic cost per cubic meter. Accordingly, all six mixes in this case study appear to have “very low” global warming potential and cumulative energy demand. The costs of all mixes are also “low” except for mix 1 and mix 4 which are normal.

3.3.2. Sensitivity analysis

In order to account for the uncertainty of the data, it is recommended to perform a sensitivity analysis on the most significant input variables of the study. In this study, there were two main variables in the mix design, the W/P ratio and the % replacement of FA with EAFS as a precursor. Hence, a sensitivity analysis was designed to calculate the effect of changing the transportation distance and market price of the FA and slag on the resulting ECO₂ index score. Varying each of the three chosen variables by ± 50% resulted in minimal (1–2%) impact on the ECO₂ index score of the studied variables, which shows that the results and conclusions are consolidated.

4. Conclusions

This paper analyses the sustainability of a promising concrete alternative, namely EAFS-based AAC. Preliminary investigation of the available literature showed that there are few studies on the performance of the material and none on its environmental and economic impacts. Hence, this paper targeted the assessment of several EAFS AAC alternatives through a concrete sustainability assessment framework previously suggested by the authors; the ECO₂ framework.

Several AAC mixes were designed to test the effect of changing the precursor from FA to EAFS and changing the water: precursor

ratio on three sustainability pillars: technical performance, environmental and economic impact. The tests performed on the AAC mixes were slump, compressive strength, chloride penetration and carbonation. After that, data from the test results as well as the site-specific environmental and economic properties was collected and the sustainability of the alternatives were compared according to the ECO₂ framework.

The preliminary conclusion was that, due to the deteriorated functional properties of the EAFS-based AAC mixes, the optimum mixes were those with FA only. However, this was only valid in terms of reinforced concrete, because when a scenario with plain concrete was assumed, the EAFS-based mixes exhibited a significantly improved sustainability potential using the ECO₂ index. This could be primarily attributed to the low cost and environmental impact (almost negligible) of the EAFS. In both cases, the original hypothesis concerning the effect of W/P ratio was proven and the results from both scenarios were run against the sensitivity of some input data and showed minimal effect.

Due to the complexity of the sustainability assessment calculations, it would not have been easy for users to analyse the optimum mix based on the combined functional, environmental and economic impacts. Hence, the use of the ECO₂ framework was critical to make this assessment easier and allow for the optimization of the mixing proportions of AAC mixes with a target of the highest achievable single sustainability score.

CRedit authorship contribution statement

Hisham Hafez: Conceptualization, Methodology, Investigation, Writing - original draft. **Dany Kassim:** Investigation. **Rawaz Kurda:** Conceptualization, Methodology, Supervision. **Rui Vasco Silva:** Conceptualization, Methodology, Project administration, Resources, Supervision, Formal analysis, Funding acquisition, Writing - review & editing. **Jorge Brito:** Supervision, Writing - review & editing.

Declaration of Competing Interest

The authors declare that they have no known competing financial interests or personal relationships that could have appeared to influence the work reported in this paper.

Acknowledgments

The authors gratefully acknowledge the support of the Portuguese Foundation for Science and Technology and CERIS Research Institute, Instituto Superior Técnico, Universidade de Lisboa.

References

- [1] P.J. Monteiro, S.A. Miller, A. Horvath, Towards sustainable concrete, *Nat. Mater.* 16 (7) (2017) 698–699, <https://doi.org/10.1038/nmat4930>.
- [2] N. Serres, S. Braymand, F. Feugeas, Environmental evaluation of concrete made from recycled concrete aggregate implementing life cycle assessment, *Journal of Building Engineering* 5 (2016) 24–33, <https://doi.org/10.1016/j.jobe.2015.11.004>.
- [3] F. Colangelo, A. Forcina, I. Farina, A. Petrillo, Life cycle assessment (LCA) of different kinds of concrete containing waste for sustainable construction, *Buildings* 8 (5) (2018) 70, <https://doi.org/10.3390/buildings8050070>.
- [4] G. Habert, J.B. d'Espinose de Lacaillerie, N. Roussel, An environmental evaluation of geopolymer based concrete production: reviewing current research trends, *J. Cleaner Prod.* 19 (11) (2011) 1229–1238, <https://doi.org/10.1016/j.jclepro.2011.03.012>.
- [5] M.F. Ashby, *Materials and the environment: Eco-informed material choice*, Elsevier Science, Ch 10, 2012.
- [6] S.A. Miller, P.J.M. Monteiro, C.P. Ostertag, A. Horvath, Concrete mixture proportioning for desired strength and reduced global warming potential, *Constr. Build. Mater.* 128 (2016) 410–421, <https://doi.org/10.1016/j.conbuildmat.2016.10.081>.
- [7] S. Yuli, D. Guan, H. Zheng, J. Ou, Y. Li, J. Meng, Z. Mi, Z. Liu, Q. Zhang, China CO₂ emission accounts 1997–2015, *Sci. Data* 5 (2018) 170–201, <https://doi.org/10.1038/sdata.2017.201>.
- [8] S.A. Miller, V.M. John, S.A. Pacca, A. Horvath, Carbon dioxide reduction potential in the global cement industry by 2050, *Cem. Concr. Res.* 114 (2018) 115–124, <https://doi.org/10.1016/j.cemconres.2017.08.026>.
- [9] F. Puertas, M. Palacios, H. Manzano, J.S. Dolado, A. Rico, J. Rodríguez, A model for the C-A-S-H gel formed in alkali-activated slag cements, *J. Eur. Ceram. Soc.* 31 (12) (2011) 2043–2056, <https://doi.org/10.1016/j.jeurceramsoc.2011.04.036>.
- [10] M. Nasir, O.S.B. Al-Amoudi, M. Maslehuddin, Effect of placement temperature and curing method on plastic shrinkage of plain and pozzolanic cement concretes under hot weather, *Constr. Build. Mater.* 152 (2017) 943–953, <https://doi.org/10.1016/j.conbuildmat.2017.07.068>.
- [11] R. Navarro, E. Zornoza, P. Garcés, I. Sánchez, E.G. Alcocel, Optimization of the alkali activation conditions of ground granulated SiMn slag, *Constr. Build. Mater.* 150 (2017) 781–791, <https://doi.org/10.1016/j.conbuildmat.2017.06.064>.
- [12] J.L. Provis, K. Arbi, S.A. Bernal, D. Bondar, A. Buchwald, A. Castel, S. Chithiraputhiran, M. Cyr, A. Dehghan, K. Dombrowski-Daube, A. Dubey, V. Ducman, G.J.G. Gluth, S. Nanukuttan, K. Peterson, F. Puertas, A. van Riessen, M. Torres-Carrasco, G. Ye, Y. Zuo, RILEM TC 247-DTA round robin test: mix design and reproducibility of compressive strength of alkali-activated concretes, *Mater. Struct.* 52 (5) (2019), <https://doi.org/10.1617/s11527-019-1396-z>.
- [13] B. Lothenbach, K. Scrivener, R.D. Hooton, Supplementary cementitious materials, *Cem. Concr. Res.* 41 (12) (2011) 1244–1256, <https://doi.org/10.1016/j.cemconres.2010.12.001>.
- [14] F. Puertas, S. Martínez-Ramírez, S. Alonso, T. Vázquez, Alkali-activated fly ash/slag cements: strength behaviour and hydration products, *Cem. Concr. Res.* 30 (10) (2000) 1625–1632, [https://doi.org/10.1016/S0008-8846\(00\)00298-2](https://doi.org/10.1016/S0008-8846(00)00298-2).
- [15] A.M. Rashad, A synopsis of carbonation of alkali-activated materials, *Green Mater.* 7 (3) (2019) 118–136, <https://doi.org/10.1680/jgrma.18.00052>.
- [16] R. Kumar, S. Kumar, S.P. Mehrotra, Towards sustainable solutions for fly ash through mechanical activation, *Resour. Conserv. Recycl.* 52 (2) (2007) 157–179, <https://doi.org/10.1016/j.resconrec.2007.06.007>.
- [17] P. Duxson, J.L. Provis, G.C. Lukey, S.W. Mallicoate, W.M. Kriven, J.S.J. Van Deventer, Understanding the relationship between geopolymer composition, microstructure and mechanical properties, *Colloids Surf., A* 269 (1–3) (2005) 47–58, <https://doi.org/10.1016/j.colsurfa.2005.06.060>.
- [18] D. Ravikumar, N. Neithalath, Electrically induced chloride ion transport in alkali activated slag concretes and the influence of microstructure, *Cem. Concr. Res.* 47 (2013) 31–42, <https://doi.org/10.1016/j.cemconres.2013.01.007>.
- [19] S.A. Bernal, R. San Nicolas, J.L. Provis, R. Mejía de Gutiérrez, J.S.J. van Deventer, Natural carbonation of aged alkali-activated slag concretes, *Mater. Struct.* 47 (4) (2014) 693–707, <https://doi.org/10.1617/s11527-013-0089-2>.
- [20] M. Nasir, M.A.M. Johari, M.O. Yusuf, M. Maslehuddin, M.A. Al-Harathi, Synthesis of alkali-activated binary blended silico-manganese fume and ground blast furnace slag mortar, *J. Adv. Concr. Technol.* 17 (12) (2019) 728–735, <https://doi.org/10.3151/jact.17.728>.
- [21] M. Nasir, M.A.M. Johari, M.O. Yusuf, M. Maslehuddin, M.A. Al-Harathi, H. Dafalla, Impact of slag content and curing methods on the strength of alkaline-activated silico-manganese fume/blast furnace slag mortars, *Arabian Journal for Science and Engineering* 44 (10) (2019) 8325–8335, <https://doi.org/10.1007/s13369-019-04063-7>.
- [22] M. Nasir, M.A.M. Johari, M. Maslehuddin, M.O. Yusuf, M.A. Al-Harathi, Influence of heat curing period and temperature on the strength of silico-manganese fume-blast furnace slag-based alkali-activated mortar, *Constr. Build. Mater.* 251 (2020) 118961, <https://doi.org/10.1016/j.conbuildmat.2020.118961>.
- [23] M. Jiang, X. Chen, F. Rajabipour, C.T. Hendrickson, Comparative life cycle assessment of conventional, glass powder, and alkali-activated slag concrete and mortar, *J. Infrastruct. Syst.* 20 (4) (2014) 401–420, [https://doi.org/10.1061/\(ASCE\)IS.1943-555X.0000211](https://doi.org/10.1061/(ASCE)IS.1943-555X.0000211).
- [24] J.L. Provis, Geopolymers and other alkali activated materials: why, how, and what?, *Mater. Struct.* 47 (1–2) (2014) 11–25, <https://doi.org/10.1617/s11527-013-0211-5>.
- [25] I. García-Lodeiro, A. Fernández-Jimenez, P. Pena, A. Palomo, Alkaline activation of synthetic aluminosilicate glass, *Ceram. Int.* 40 (4) (2014) 5547–5558, <https://doi.org/10.1016/j.ceramint.2013.10.146>.
- [26] M. Komljenovi, Z. Baarevi, N. Marjanovi, V. Nikoli, External sulfate attack on alkali-activated slag, *Constr. Build. Mater.* 49 (2013) 31–39, <https://doi.org/10.1016/j.conbuildmat.2013.08.013>.
- [27] A. Passuello, E.D. Rodríguez, E. Hirt, M. Longhi, S.A. Bernal, J.L. Provis, A.P. Kirchheim, Evaluation of the potential improvement in the environmental footprint of geopolymers using waste-derived activators, *J. Cleaner Prod.* 166 (2017) 680–689, <https://doi.org/10.1016/j.jclepro.2017.08.007>.
- [28] Y. Jiang, T.C. Ling, C. Shi, S.Y. Pan, Characteristics of steel slags and their use in cement and concrete—A review, *Resour. Conserv. Recycl.* 136 (2018) 187–197, <https://doi.org/10.1016/j.resconrec.2018.04.023>.
- [29] Bigozzi, M.C., Sandrolini, F., Andreola, F., Barbieri, L. and Lancellotti, I., 2010, June. Recycling electric arc furnace slag as unconventional component for building materials. Proceedings of 2nd International Conference on sustainable construction materials and technologies. Ancona, Italy , 557–567.
- [30] E. Adesanya, H. Sreenivasan, A.M. Kantola, V.V. Telkki, K. Ohenoja, P. Kinnunen, M. Illikainen, Ladle slag cement-Characterization of hydration and conversion, *Constr. Build. Mater.* 193 (2018) 128–134, <https://doi.org/10.1016/j.conbuildmat.2018.10.179>.

- [31] I. Arribas, A. Santamaria, E. Ruiz, V. Ortega-Lopez, J.M. Manso, Electric arc furnace slag and its use in hydraulic concrete, *Constr. Build. Mater.* 90 (2015) 68–79, <https://doi.org/10.1016/j.conbuildmat.2015.05.003>.
- [32] S. Choi, J.M. Kim, D. Han, J.H. Kim, Hydration properties of ladle furnace slag powder rapidly cooled by air, *Constr. Build. Mater.* 113 (2016) 682–690, <https://doi.org/10.1016/j.conbuildmat.2016.03.089>.
- [33] L. Coppola, A. Buoso, D. Coffetti, P. Kara, S. Lorenzi, Electric arc furnace granulated slag for sustainable concrete, *Constr. Build. Mater.* 123 (2016) 115–119, <https://doi.org/10.1016/j.conbuildmat.2016.06.142>.
- [34] M.A. González-Ortega, S.H.P. Cavalaro, G.R. de Sensale, A. Aguado, Durability of concrete with electric arc furnace slag aggregate, *Constr. Build. Mater.* 217 (2019) 543–556, <https://doi.org/10.1016/j.conbuildmat.2019.05.082>.
- [35] F. Faleschini, M.A. Fernández-Ruiz, M.A. Zanini, K. Brunelli, C. Pellegrino, E. Hernández-Montes, High performance concrete with electric arc furnace slag as aggregate: mechanical and durability properties, *Constr. Build. Mater.* 101 (2015) 113–121, <https://doi.org/10.1016/j.conbuildmat.2015.10.022>.
- [36] M.E. Parron-Rubio, F. Perez-García, A. Gonzalez-Herrera, M.D. Rubio-Cintas, Concrete properties comparison when substituting a 25% cement with slag from different provenances, *Materials* 11 (6) (2018) 1029, <https://doi.org/10.3390/ma11061029>.
- [37] E.E. Hekal, S.A. Abo-El-Enein, S.A. El-Korashy, G.M. Megahed, T.M. El-Sayed, Hydration characteristics of Portland cement-Electric arc furnace slag blends, *HBRC Journal* 9 (2) (2013) 118–124, <https://doi.org/10.1016/j.hbrj.2013.05.006>.
- [38] M.N. Amin, K. Khan, M.U. Saleem, N. Khurram, M.U.K. Niazi, Influence of mechanically activated electric arc furnace slag on compressive strength of mortars incorporating curing moisture and temperature effects, *Sustainability* 9 (8) (2017) 1178, <https://doi.org/10.3390/su9081178>.
- [39] D. Adolfsen, R. Robinson, F. Engström, B. Björkman, Influence of mineralogy on the hydraulic properties of ladle slag, *Cem. Concr. Res.* 41 (8) (2011) 865–871, <https://doi.org/10.1016/j.cemconres.2011.04.003>.
- [40] L. Muhmood, S. Vitta, D. Venkateswaran, Cementitious and pozzolanic behavior of electric arc furnace steel slags, *Cem. Concr. Res.* 39 (2) (2009) 102–109, <https://doi.org/10.1016/j.cemconres.2008.11.002>.
- [41] S. Apithanyasai, P. Nooak, N. Supakata, The utilization of concrete residue with electric arc furnace slag in the production of geopolymer bricks, *Engineering Journal* 22 (1) (2018) 1–14, <https://doi.org/10.4186/ej.2018.22.1.10.4186/ej.2018.22.1.1>.
- [42] M. Ozturk, M.B. Bankir, O.S. Bolukbasi, U.K. Sevim, Alkali activation of electric arc furnace slag: Mechanical properties and micro analyzes, *Journal of Building Engineering* 21 (2019) 97–105, <https://doi.org/10.1016/j.job.2018.10.005>.
- [43] H. Hafez, R. Kurda, N. Al-Ayish, T. Garcia-Segura, W.M. Cheung, B. Nagaratnam, in: Zhen Leng (Ed.), *A whole life cycle performance-based ECONomic and ECOlogical assessment framework (ECO₂) for concrete sustainability*, 292, *Journal of Cleaner Production*, UK, 2021.
- [44] ASTM C33, ASTM C33 standard specifications for concrete aggregates, *ASTM Standard Book* (2003).
- [45] N.P. En, 12350–2. Testing fresh concrete. Part 2: slump test, IPQ, Lisbon, Portugal 11 (2009) p.
- [46] N.P. En, 12390–3. Testing hardened concrete. Part 3: compressive strength of test specimens, IPQ, Lisbon, Portugal 21 (2009) p.
- [47] N.T. Build, 492., Concrete, mortar and cement-based repair materials: Chloride migration coefficient from non-steady state migration experiments, Nordtest, Espoo, Finland, 1991.
- [48] L.N.E.C. E 391. 1993. Concretes: Determination of the carbonation resistance (in Portuguese), Lisbon, Portugal
- [49] H. Hafez, R. Kurda, W.M. Cheung, B. Nagaratnam, A systematic review of the discrepancies of life cycle assessments of green concrete, *Applied Sciences* 9 (22) (2019) 4803, <https://doi.org/10.3390/app9224803>.
- [50] G. Markset, M. Kioumars, Need for further development in service life modelling of concrete structures in chloride environment, *Procedia Eng.* 171 (2017) 549–556, <https://doi.org/10.1016/j.proeng.2017.01.37>.
- [51] Rawaz Kurda, Jorge de Brito, José D. Silvestre, CONCRETOP – A multi-criteria decision method for concrete optimization, *Environ. Impact Assess. Rev.* 74 (2019) 73–85, <https://doi.org/10.1016/j.eiar.2018.10.006>.